



# SPRING MATERIALS

## SIZES & STRENGTH VALUES

### ISSUE 11

English / US

October 4, 2023



# Table of Contents

## **Alloy Steel**

Music Wire - ASTM A228 UNS# K08500 & G10860	1
--	---

## **High Carbon Steel Wire/Bar**

Oil Tempered Wire (Class I) - ASTM A229 UNS# K07001 & G10650	2
---	---

Chrome Vanadium Wire - ASTM A231 UNS# G92540	3
---	---

Chrome Silicon Wire - ASTM A401 UNS# G92540	4
--	---

## **Hot Rolled Alloy Bar**

Hot Rolled Alloy Bar, 5160-H, 51B60-H, 4161-H, ASTM 689 UNS# H51601 & H51600	5
---	---

## **Stainless Steel Wire/Bar**

Type 302 Stainless Steel Wire - ASTM A313 - AMS 5688 UNS# S30200	6
---	---

Type 316 Stainless Steel Wire - ASTM A313 UNS# S31600	8
--	---

Type T-316 Stainless Steel Bar - ASTM A313 UNS# S31600	9
---	---

17-7PH/17-4PH Stainless Steel Wire - ASTM A313 - UNS# S17700	10
---	----

Type 17-4 Bar - ASTM A564 UNS# S17400	11
--	----

Alloy 20 Spring Tempered - ASTM B471 UNS# N08020	12
---	----

A286 Alloy Spring Tempered Wire – AMS 5734	13
--	----

## **Copper Base Alloy Wire**

Phosphor Bronze, Grade A, ASTM B159	14
Beryllium Copper, ASTM B197	15

## **Nickel Base Alloy Wire/Bar**

Inconel X750 Spring Tempered Wire - AMS 5699 UNS# N07750	16
Type Inconel X750 Bar - ASTM B637 Grade 688 UNS# N07500	17
Inconel 600 Spring Tempered Wire - Q Q-W-390 UNS# N06600	18
Inconel 625 Spring Tempered - ASTM B446 UNS# N06625	19
Inconel 718 Spring Tempered Wire - ASTM B637 UNS# N07718	20
Inconel 718 Bar - ASTM B637 UNS# N07718	21
MP35N Spring Tempered Wire - AMS 5844 UNS# R30035	22
Elgiloy Spring Tempered Wire - AMS 5833 UNS# R30003	23
Monel 400 Spring Tempered - ASTM B164 UNS# N04400	24
Monel K-500 Spring Tempered - ASTM 4676 UNS# N05500	25
Hastelloy C-276 Spring Tempered - ASTM B574 (Chem. only) UNS# N10276	26
Hastelloy B-2 Spring Tempered - ASTM B335 UNS# N10665	27

## **Titanium**


Titanium Beta-C Spring Tempered Wire - AMS 4957  
UNS# R58640 28

Titanium 6Al-4V Spring Tempered Wire - AMS 4957  
UNS# R58640 29

## **Tool Steel**

H-12 Tungsten Wire/Bar - ASTM A681  
UNS# T20812 30



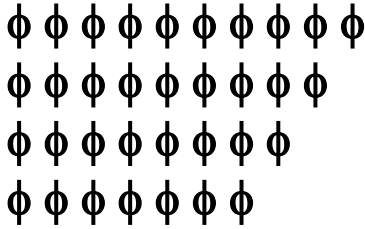

The following is provided as a reference guide only, and not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.



## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Music Wire ASTM A228 UNS K08500 & G10860	Cold drawn. Constant tensile strength. High-quality and good for high cycle spring applications.	250 °F	449/230	(E) 30 (G) 11.5	45%	.012" to .250"

### SIZE CHART

Wire Diameter, in							
.012	.026	.038	.054	.072	.095	.124	.192
.013	.027	.039	.055	.075	.098	.125	.207
.014	.028	.040	.056	.076	.100	.130	.225
.015	.029	.041	.057	.078	.105	.135	.243
.016	.030	.042	.058	.080	.109	.138	.250*
.017	.031	.044	.059	.082	.110	.148	
.018	.032	.045	.062	.085	.112	.156	
.020	.033	.047	.063	.090	.113	.162	
.022	.035	.048	.065	.091	.114	.170	
.024	.036	.050	.067	.093	.118	.177	
.025	.037	.051	.070	.094	.120	.187	

\* Sizes up to .283 in diameter are available on request.

### TENSILE STRENGTH CHART

Diameter, in	Tensile Strength, ksi		Diameter, in	Tensile Strength, ksi		Diameter, in	Tensile Strength, ksi		Diameter, in	Tensile Strength, ksi	
	min	max		min	max		min	max		min	max
.004	439	485	.022	345	382	.059	296	327	.125	261	288
.005	426	471	.024	341	377	.063	293	324	.130	259	286
.006	415	459	.026	337	373	.067	290	321	.135	258	285
.007	407	449	.028	333	368	.072	287	317	.140	256	283
.008	399	441	.030	330	365	.076	284	314	.145	254	281
.009	393	434	.032	327	361	.080	282	312	.150	253	279
.010	387	428	.034	324	358	.085	279	308	.156	251	277
.011	382	422	.036	321	355	.090	276	305	.162	249	275
.012	377	417	.038	318	352	.095	274	303	.177	245	270
.013	373	412	.040	315	349	.100	271	300	.192	241	267
.014	369	408	.042	313	346	.102	270	299	.207	238	264
.015	365	404	.045	309	342	.107	268	296	.225	235	260
.016	362	400	.048	306	339	.110	267	295	.250	230	255
.018	356	393	.051	303	335	.112	266	294			
.020	350	387	.055	300	331	.121	263	290			

Tensile strength values for intermediate diameters may be interpolated.

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.



## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range, ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Oil Tempered Wire, Class I ASTM A229 UNS K07001 & G10650	Cold drawn. All purpose spring material. Heat treated before fabrication. Susceptible to hydrogen embrittlement when plated.	250 °F	323/125 (class I)	(E) 30 (G) 11.5	45%	.032" to .625"

### SIZE CHART

Wire Diameter, in							
.032	.067	.099	.135	.180	.250	.306	.468
.035	.072	.100	.148	.187	.262	.312	.500
.040	.080	.105	.156	.192	.263	.331	.531
.041	.086	.113	.162	.207	.281	.343	.562
.047	.087	.120	.170	.225	.283	.362	.625
.051	.091	.125	.172	.235	.295	.406	
.058	.093	.128	.177	.243	.302	.437	

### TENSILE STRENGTH CHART

Diameter, in	Tensile Strength, ksi				Diameter, in	Tensile Strength, ksi			
	Class I		Class II			Class I		Class II	
	min	max	min	max		min	max	min	max
.020	293	323	324	354	.135	215	240	241	266
.023	289	319	320	350	.148	210	235	236	261
.026	286	316	317	347	.162	205	230	231	256
.029	283	313	314	344	.177	200	225	226	251
.032	280	310	311	335	.192	195	220	221	246
.035	274	304	305	335	.207	190	215	216	241
.041	266	296	297	327	.225	188	213	214	239
.048	259	289	290	320	.244	187	212	213	238
.054	253	283	284	314	.250	185	210	211	236
.062	247	277	278	308	.312	183	208	209	234
.072	241	271	272	302	.375	180	205	206	231
.080	235	265	266	296	.438	175	200	201	226
.092	230	260	261	291	.500	170	195	196	221
.106	225	255	256	286	.562	165	190	191	216
.120	220	250	251	281	.625	165	190	191	216

Tensile strength values for intermediate diameters may be interpolated.

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range, ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Chrome Vanadium ASTM A-231 Valve Quality: ASTM A-232 AMS 6450	Cold drawn. Good for shock loads and medium elevated temperature applications. Susceptible to hydrogen embrittlement when plated.	425°F	325/190	(E) 30 (G) 11.5	45%	.043" to .500"

### SIZE CHART

Wire Dia., in.	Wire Dia., in.	Wire Dia., in.	Wire Dia., in.	Wire Dia., in.	Wire Dia., in.	Wire Dia., in.	Wire Dia., in.
.043	.060	.091	.102	.125	.207	.312	.406
.046	.062	.092	.105	.135	.225	.331	.437
.054	.072	.095	.113	.162	.262	.343	.468
.059	.080	.099	.120	.187	.283	.375	
<b>Valve Quality</b>							
<b>Wire Diameter, in</b>							
.059	.095	.135	.162	.207	.283	.343	
.085	.109	.142	.177	.243	.306		
.090	.125	.148	.192	.262	.331		

### TENSILE STRENGTH CHART

Diameter, inches	Tensile Strength, ksi <sup>A</sup>		Reduction of Area, minimum, %	Diameter, inches	Tensile Strength, ksi <sup>A</sup>		Reduction of Area, minimum, %
	minimum	maximum			minimum	maximum	
.020	300	325	C	.162	225	245	40
.032	290	315	C	.192	220	240	40
.041	280	305	C	.244	210	230	40
.054	270	295	C	.283	205	225	40
.062	265	290	C	.312	203	223	40
.080	255	275	C	.375	200	220	40
.105	245	265	45	.438	195	215	40
.135	235	255	45	.500	190	210	40

A Tensile strength values for intermediate diameters may be interpolated.

C The reduction of area test is not applicable to wire diameters under 0.092in.

Note: Valve quality material has improved surface quality.

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range, ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Chrome Silicon ASTM A401 UNS G92540	Cold drawn. Good for shock loads and medium elevated temperature applications. Susceptible to hydrogen embrittlement when plated.	475°F	300/226	(E) 30 (G) 11.5	45%	.024" to .625"

### SIZE CHART

Wire Diameter, in							
.024	.041	.056	.085	.109	.177	.306	.500
.025	.042	.057	.088	.113	.180	.312	.531
.028	.043	.058	.089	.120	.187	.331	.562
.029	.044	.062	.090	.125	.192	.343	.594
.030	.045	.065	.091	.128	.207	.362	.625
.031	.046	.067	.092	.135	.218	.375	
.033	.047	.072	.093	.142	.225	.394	
.034	.049	.075	.095	.148	.234	.406	
.036	.050	.076	.098	.156	.243	.421	
.037	.051	.078	.100	.162	.250	.437	
.038	.053	.080	.102	.167	.262	.453	
.039	.054	.083	.105	.170	.281	.468	

### TENSILE STRENGTH CHART

Diameter, in <sup>A</sup>	Tensile Strength, ksi		Reduction of Area, min, %	Diameter, in <sup>A</sup>	Tensile Strength, ksi		Reduction of Area, min, %
	minimum	maximum			minimum	maximum	
.032	300	325	C	.192	260	283	40
.041	298	323	C	.219	255	278	40
.054	292	317	C	.250	250	275	40
.062	290	315	C	.312	245	270	40
.080	285	310	C	.375	240	265	40
.092	280	305	45	.438	235	260	35
.120	275	300	45	.500	230	255	35
.135	270	295	40	.562	228	253	30
.162	265	290	40	.625	226	251	30
.177	260	285	40				

A Tensile strength values for intermediate diameters may be interpolated.  
 C The reduction of area test is not applicable to wire under 0.105 in. in diameter  
 Preferred sizes. For a complete list, refer to ANSI B32.4.

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range, ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, inches
5160-H .ASTM A689, A29 UNS G51600	Hot-rolled special bar quality, fine grained. Good fatigue life.	400 °F	242/211	(E) 29 (G) 10.5	45%	.468" to 1.25"

Bar Diameter, in					
.468	.625	.781	.937	1.125	
.500	.656	.812	.968	1.187	
.531	.687	.843	1.000	1.250	
.562	.718	.875	1.032		
.593	.750	.906	1.062		

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range, ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, inches
51B60-H ASTM A689, A29 UNS 51601	Hot-rolled special bar quality, fine grained. Good fatigue life.	400 °F	242/211	(E) 30 (G) 11.0	45%	1.25" to 1.937"

Bar Diameter, in					
1.250	1.437	1.625	1.812	1.937	
1.312	1.500	1.687	1.843		
1.375	1.562	1.750	1.875		

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range, ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, inches
4161-H ASTM A689, A29 UNS 41610	Hot-rolled special bar quality, fine grained. Good fatigue life.	400 °F	242/211	(E) 30 (G) 11.0	45%	2.00" to 2.875"

Bar Diameter, in					
2.000	2.375	2.562	2.750		
2.125	2.437	2.625	2.812		
2.250	2.500	2.687	2.875		

COMMENTS FOR ALL ALLOYS:					
Material is produced in the "As Rolled" condition. Springs are manufactured via the Hot Wound procedure, quenched and tempered. Each spring is checked for Rockwell Hardness to insure the proper temper is achieved. Temper hardness should range between HRC 41 and HRC 49.					
If the hardness exceeds HRC 49, brittle properties could be produced, increasing failure possibilities.					
Bar lengths in general range from 40' to 45'.					
HRC 41 = 187,000 psi tensile			HRC 49 = 253,000 psi tensile		
<b>Note: Virtually all Hot Rolled Alloy Bar stocked by Suhm is turned and polished.</b>					

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range (ksi min)	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes (inches)
AISI 302/304 Stainless Steel Wire ASTM A313 AMS 5688 UNS S30200	Cold drawn. Low cost. Good for general purpose corrosion and elevated temperature applications. Has some magnetism in a spring temper.	500°F	325/130	(E) 28 (G) 9.8	40%	.015" to .500"

### SIZE CHART

Wire Diameter, in						
.015	.033	.052	.072	.094	.138	.244
.016	.034	.053	.074	.095	.140	.250
.017	.035	.054	.075	.097	.142	.262
.018	.036	.055	.076	.098	.148	.282
.019	.037	.056	.077	.099	.156	.297
.020	.038	.057	.078	.100	.162	.306
.021	.039	.058	.080	.102	.170	.312
.022	.040	.059	.082	.105	.172	.331
.023	.041	.060	.083	.109	.177	.343
.024	.042	.061	.084	.112	.179	.362
.025	.043	.062	.085	.113	.180	.375
.026	.044	.064	.086	.115	.182	.393
.027	.045	.065	.088	.118	.187	.406
.028	.046	.067	.089	.120	.192	.437
.029	.047	.068	.090	.125	.207	.468
.030	.049	.069	.091	.128	.218	.500
.031	.050	.070	.092	.129	.225	.562
.032	.051	.071	.093	.135	.234	

### TENSILE STRENGTH CHART

Diameter, in <sup>A</sup>	Tensile Strength, psi	
	minimum	maximum
Up to 0.009 incl.	325,000	355,000
Over 0.009 to 0.010 incl.	320,000	350,000
Over 0.010 to 0.011 incl.	318,000	348,000
Over 0.011 to 0.012 incl.	316,000	346,000
Over 0.012 to 0.013 incl.	314,000	344,000
Over 0.013 to 0.014 incl.	312,000	342,000
Over 0.014 to 0.015 incl.	310,000	340,000
Over 0.015 to 0.016 incl.	308,000	338,000
Over 0.016 to 0.017 incl.	306,000	336,000
Over 0.017 to 0.018 incl.	304,000	334,000
Over 0.018 to 0.020 incl.	300,000	330,000
Over 0.020 to 0.022 incl.	296,000	326,000
Over 0.022 to 0.024 incl.	292,000	322,000
Over 0.024 to 0.026 incl.	291,000	320,000
Over 0.026 to 0.028 incl.	289,000	318,000
Over 0.028 to 0.031 incl.	285,000	315,000
Over 0.031 to 0.034 incl.	282,000	310,000
Over 0.034 to 0.037 incl.	280,000	308,000
Over 0.037 to 0.041 incl.	275,000	304,000
Over 0.041 to 0.045 incl.	272,000	300,000
Over 0.045 to 0.050 incl.	267,000	295,000
Over 0.050 to 0.054 incl.	265,000	293,000

Over 0.054 to 0.058 incl.	261,000	289,000
Over 0.058 to 0.063 incl.	258,000	285,000
Over 0.063 to 0.070 incl.	252,000	281,000
Over 0.070 to 0.075 incl.	250,000	278,000
Over 0.075 to 0.080 incl.	246,000	275,000
Over 0.080 to 0.087 incl.	242,000	271,000
Over 0.087 to 0.095 incl.	238,000	268,000
Over 0.095 to 0.105 incl.	232,000	262,000
Over 0.105 to 0.115 incl.	227,000	257,000
Over 0.115 to 0.125 incl.	222,000	253,000
Over 0.125 to 0.135 incl.	217,000	248,000
Over 0.135 to 0.148 incl.	210,000	241,000
Over 0.148 to 0.162 incl.	205,000	235,000
Over 0.162 to 0.177 incl.	198,000	228,000
Over 0.177 to 0.192 incl.	194,000	225,000
Over 0.192 to 0.207 incl.	188,000	220,000
Over 0.207 to 0.225 incl.	182,000	214,000
Over 0.225 to 0.250 incl.	175,000	205,000
Over 0.250 to 0.278 incl.	168,000	198,000
Over 0.278 to 0.306 incl.	161,000	192,000
Over 0.306 to 0.331 incl.	155,000	186,000
Over 0.331 to 0.362 incl.	150,000	180,000
Over 0.362 to 0.394 incl.	145,000	175,000
Over 0.394 to 0.438 incl.	140,000	170,000
Over 0.436 to 0.500 incl.	135,000	165,000
Over 0.500	130,000	160,000

A Tensile strength values for intermediate diameters may be interpolated.

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range (ksi min)	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes (inches)
AISI 316 Stainless Steel Wire ASTM A313 UNS S31600	Cold drawn. Better corrosion resistance than 302/304. Good for elevated temperatures. No magnetism.	550 °F	245/110	(E) 28 (G) 9.8	40%	.017" to .500"

### SIZE CHART

Wire Diameter, in									
.017	.029	.039	.051	.067	.085	.105	.142	.218	.312
.018	.030	.040	.054	.068	.086	.106	.148	.225	.331
.020	.031	.041	.055	.070	.088	.109	.156	.234	.343
.022	.032	.042	.056	.072	.090	.112	.162	.250	.362
.023	.033	.043	.057	.076	.091	.115	.172	.262	.375
.024	.034	.044	.058	.078	.094	.118	.177	.282	.406
.025	.035	.045	.059	.080	.095	.120	.187	.283	.437
.026	.036	.047	.060	.082	.098	.125	.192	.292	.468
.027	.037	.049	.062	.083	.100	.135	.203	.300	.500
.028	.038	.050	.065	.084	.101	.138	.207	.306	.562

### TENSILE STRENGTH CHART

Diameter, in	Tensile Strength, psi <sup>A</sup>	
	minimum	maximum
Up to 0.010 incl.	245,000	275,000
Over 0.010 to 0.015 incl.	240,000	270,000
Over 0.015 to 0.024 incl.	235,000	265,000
Over 0.024 to 0.041 incl.	235,000	265,000
Over 0.041 to 0.047 incl.	230,000	260,000
Over 0.047 to 0.054 incl.	225,000	255,000
Over 0.054 to 0.062 incl.	220,000	250,000
Over 0.062 to 0.072 incl.	215,000	245,000
Over 0.072 to 0.080 incl.	210,000	240,000
Over 0.080 to 0.092 incl.	205,000	235,000
Over 0.092 to 0.105 incl.	200,000	230,000
Over 0.105 to 0.120 incl.	195,000	225,000
Over 0.120 to 0.148 incl.	185,000	215,000
Over 0.148 to 0.166 incl.	180,000	210,000
Over 0.166 to 0.177 incl.	170,000	200,000
Over 0.177 to 0.207 incl.	160,000	190,000
Over 0.207 to 0.225 incl.	155,000	185,000
Over 0.225 to 0.250 incl.	150,000	180,000
Over 0.250 to 0.312 incl.	140,000	170,000
Over 0.312 to 0.375 incl.	135,000	165,000
Over 0.375 to 0.500 incl.	130,000	160,000
Over 0.500	125,000	155,000

<sup>A</sup> When wire is specified as straightened and in cut lengths, the minimum tensile strength shall be 90% of the value listed in the table.

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range, ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
T-316 Stainless Steel Bar ASTM A276 Cond B UNS S31600	Cold drawn. Better corrosion resistance than 302/304. Good for elevated temperatures. No magnetism.	550 °F	245/11	(E) 28 (G) 9.8	40%	.562" to 1.750"

### SIZE CHART

Bar Diameter, in							
.562	.656	.812	.938	1.063	1.250	1.438	1.625
.593	.687	.875	.968	1.125	1.313	1.500	1.750
.625	.750	.906	1.000	1.188	1.375	1.562	

### TENSILE STRENGTH CHART

Diameter, in.	Tensile Strength, ksi minimum	Elongation in 2 in. or 4D, minimum %	Reduction of Area, minimum, %
up to 0.750	125	12	35
over 0.750 to 1.000	115	15	35
over 1.000 to 1.250	105	20	35
over 1.250 to 1.500	100	24	45
over 1.500 to 1.750	95	28	45

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.



## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range (ksi min)	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
17-7PH Stainless Steel Wire ASTM A313 Type 631 UNS S17700 Condition C	Cold drawn. Good for elevated temperatures. No magnetism.	600°F	365/203	(E) 29 (G) 11.0	45%	.017" to .562"

### SIZE CHART

Wire Diameter, in									
.017	.029	.039	.051	.067	.085	.105	.142	.218	.312
.018	.030	.040	.054	.068	.086	.106	.148	.225	.331
.020	.031	.041	.055	.070	.088	.109	.156	.234	.343
.022	.032	.042	.056	.072	.090	.112	.162	.250	.362
.023	.033	.043	.057	.076	.091	.115	.172	.262	.375
.024	.034	.044	.058	.078	.094	.118	.177	.282	.406
.025	.035	.045	.059	.080	.095	.120	.187	.283	.437
.026	.036	.047	.060	.082	.098	.125	.192	.292	.468
.027	.037	.049	.062	.083	.100	.135	.203	.300	.500
.028	.038	.050	.065	.084	.101	.138	.207	.306	.562

### TENSILE STRENGTH CHART

Diameter, in.(mm)	Tensile Strength		
	Cold Drawn Condition C, psi nominal	Condition CH-900 <sup>B</sup> , psi, minimum	Condition CH-900 <sup>B</sup> , psi, maximum
0.010 to 0.015 incl.	295,000	335,000	365,000
Over 0.015 to 0.020 incl.	290,000	330,000	360,000
Over 0.020 to 0.029 incl.	285,000	325,000	355,000
Over 0.029 to 0.041 incl.	270,000	310,000	340,000
Over 0.051 to 0.061 incl.	265,000	305,000	335,000
Over 0.061 to 0.071 incl.	257,000	297,000	327,000
Over 0.071 to 0.086 incl.	255,000	292,000	322,000
Over 0.086 to 0.090 incl.	245,000	292,000	312,000
Over 0.090 to 0.100 incl.	242,000	279,000	309,000
Over 0.100 to 0.106 incl.	238,000	274,000	304,000
Over 0.106 to 0.130 incl.	236,000	272,000	302,000
Over 0.130 to 0.138 incl.	230,000	260,000	290,000
Over 0.138 to 0.146 incl.	228,000	258,000	288,000
Over 0.146 to 0.162 incl.	226,000	256,000	286,000
Over 0.162 to 0.180 incl.	224,000	254,000	284,000
Over 0.180 to 0.207 incl.	222,000	252,000	282,000
Over 0.207 to 0.225 incl.	218,000	248,000	278,000
Over 0.225 to 0.306 incl.	213,000	242,000	272,000
Over 0.306 to 0.440 incl.	207,000	235,000	265,000
Over 0.440 to 0.625 incl.	203,000	230,000	260,000

B Aged at 900° F for one hour and air cooled.

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range (ksi min)	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
17-4PH Bar ASTM A564 UNS S17400 H900	Age hardened. High tensile strength. Good for general corrosion resistance. No magnetism.	550°F	190	(E) 29 (G) 11.2	45%	.562" to 2.875"

### SIZE CHART

Bar Diameter, inches			
.562	1.125	1.688	2.313
.625	1.188	1.750	2.375
.688	1.250	1.813	2.438
.750	1.313	1.938	2.500
.812	1.375	2.000	2.563
.875	1.438	2.063	2.625
.938	1.500	2.125	2.688
1.000	1.563	2.188	2.750
1.063	1.625	2.250	2.875

#### COMMENTS:

Material is produced in the "Cold Rolled" / Annealed condition. After coiling springs should be aged to the H 900 condition. Bars with hardness value of HRC 44 will have estimated tensile of 200 KSI. As a general rule, bar lengths are 12 feet long. Some sizes are available up to 20 feet in length. Check with a Suhm representative to verify lengths.

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range, ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Alloy 20 Spring Tempered Wire ASTM B473 UNS N08020	Excellent mechanical properties and easily fabricated. Moderate to good corrosion resistance. Used extensively in petrochemical and refining applications.	-	200/125	(E) 29 (G) 10.9	45%	.025" to .362"

### SIZE CHART

Wire Diameter, in							
.025	.037	.050	.062	.077	.092	.113	.156
.026	.038	.051	.064	.078	.093	.115	.162
.027	.039	.052	.065	.080	.094	.118	.187
.028	.040	.053	.067	.082	.095	.120	.207
.029	.041	.054	.068	.083	.097	.125	.234
.030	.042	.055	.069	.084	.098	.128	.235
.031	.043	.056	.070	.085	.099	.129	.262
.032	.044	.057	.071	.086	.100	.135	.362
.033	.045	.058	.072	.088	.102	.138	
.034	.046	.059	.074	.089	.105	.140	
.035	.047	.060	.075	.090	.109	.142	
.036	.049	.061	.076	.091	.112	.148	

### TENSILE STRENGTH CHART

Diameter, in	Tensile Strength, ksi	
	minimum	maximum
Over 0.010 to 0.030	200	230
Over 0.030 to 0.060	195	225
Over 0.060 to 0.075	190	220
Over 0.075 to 0.100	185	215
Over 0.100 to 0.125	180	210
Over 0.125 to 0.140	170	200
Over 0.140 to 0.187	160	190
Over 0.187 to 0.250	150	180
Over 0.250 to 0.312	135	165
Over 0.312 to 0.375	125	155

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
A-286 Spring Tempered Wire AMS 5734 and others UNS S66286	Cold drawn. Good corrosion resistance. Good for use in elevated temperature applications.	900 °F	200/160	(E) 29.1 (G) 10.4	45%	.040" to .295"

### SIZE CHART

Wire Diameter, in		
0.040	0.148	0.250
0.093	0.150	0.295
0.125	0.207	

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Phosphor Bronze Wire Grade A ASTM B159 H08 UNS C51000	Cold drawn. Good electrical conductivity. Good corrosion resistance.	200°F	145/105	(E) 15 (G) 6.25	40%	.010" to .468"

### SIZE CHART

Wire Diameter, in							
.010	.025	.045	.072	.109	.144	.204	.468
.012	.028	.051	.080	.114	.156	.244	
.015	.032	.057	.091	.120	.162	.250	
.018	.036	.062	.095	.125	.182	.312	
.020	.040	.064	.101	.128	.187	.406	

### TENSILE STRENGTH CHART

Diameter, inches	Tensile Strength, psi, minimum	Elongation in 2 inches, %
.025 and under	145,000	....
over .025 to .0625	135,000	....
over .0625 to .125	130,000	....
over .125 to .250	125,000	....
over .250 to .375	120,000	5.0
over .375 to .500	105,000	9.0

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range, ksi min	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Beryllium Copper Wire ASTM B197	Cold drawn. Good electrical conductivity. Good corrosion resistance.	400 °F	230/150	(E) 18.5 (G) 7.2	45%	.010" to .468"

### SIZE CHART

Wire Diameter, in				
.010	.028	.052	.085	.187
.0113	.032	.055	.093	.468
.0126	.035	.057	.095	
.014	.040	.060	.099	
.016	.045	.064	.125	
.020	.050	.072	.156	
.025	.051	.080	.1645	

#### Comment

Beryllium Copper has several temper designations. The application determines which temper to use. Call your Suhm representative for details.

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Inconel X-750 Spring Tempered Wire AMS 5699 UNS N07750	Cold drawn, age hardened. Good corrosion resistance. Good for use in elevated temperature applications. Good for use in Sour-Gas applications.	700°F	230/180	(E) 29 (G) 11.2	45%	.005" to .750"

### SIZE CHART

Wire Diameter, in							
.005	.022	.044	.059	.114	.182	.281	.500
.007	.023	.045	.062	.115	.187	.295	.531
.008	.025	.047	.072	.125	.192	.312	.562
.010	.028	.050	.080	.135	.207	.331	.625
.012	.030	.051	.093	.144	.218	.343	.750
.014	.032	.052	.099	.148	.225	.362	
.015	.035	.054	.100	.156	.234	.375	
.016	.038	.055	.101	.162	.243	.406	
.018	.040	.057	.105	.172	.250	.437	
.020	.041	.058	.109	.177	.262	.468	

### SS-X750

#### Suhm Coil Spring Works Wire Specification for Inconel X-750

Suhm Spring Specification	Heat Treat	Notes
SS-X750	1200F Min. / 4 Hrs. Min	Must meet and be certified to AMS-5699E Chemicals Only, Physical Properties are to meet SS-X750. Solution Heat Treat and Original Mill Required NACE MR-01-75

#### Physical Properties for SS-X750

Sizes, in	Min. Tensile, psi	Min. Yield, psi	Min. Elong. %	Min. R of A %	HRC Max.
.005 - .125	220,000	200,000	4	20	50
.126 - .250	220,000	200,000	4	20	50
.251 - .437	210,000	190,000	6	20	50
.438 - .500	200,000	175,000	8	20	50
.501 - .750	180,000	160,000	8	20	50

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Inconel X-750 Bar ASTM B637 UNS N07500	Cold drawn. Good corrosion resistance. Good for use in elevated temperature applications. Good for use in Sour-Gas applications.	700°F	170	(E) 29 (G) 11.2	45%	.750" to 2.500"

### SIZE CHART

Bar Diameter, in			
.750	1.125	1.375	2.250
.812	1.150	1.500	2.500
.956	1.187	1.625	
.968	1.312	1.750	
1.000	1.325	2.125	

### Tensile and Hardness Requirements

Alloy	Heat Treatment	Tensile Strength, min, psi	Yield Strength (0.2% offset), min, psi	Elongation in 2 in or 4D, min, %	Reduction of Area, min, %	Brinell Hardness
N07750 Type 2 <sup>c</sup>	solution at 1800 °F + precipitation harden	170,000	115,000	18	18	302 to 363

#### COMMENTS:

Material is produced in either the solution annealed or solution annealed/aged condition. This specification only requires that minimum strength values be met. If necessary check with a Suhm representative to obtain actual capabilities for tensile and yield. Aging time and temperatures are extensive (20 Hrs. @ 1300°F) to produce the required strengths.

Bar lengths in general will average 12' to 14'; however, Suhm maintains a stocking arrangement to have available 10' - 20' lengths on some sizes. Some sizes are available in lengths up to 35'. Check with a Suhm representative to verify sizes and lengths.

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.



## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Inconel 600 QQ-W-390 UNS N06600	Cold drawn. Good corrosion resistance. Good for use in elevated temperature applications.	700 °F	205/120	(E) 29 G) 11.0	45%	.005" to .750"

### SIZE CHART

Wire Diameter, in							
.005	.014	.025	.072	.135	.192	.343	.625
.007	.015	.032	.080	.148	.207	.375	.750
.008	.017	.045	.093	.156	.225	.406	
.009	.018	.050	.105	.162	.243	.437	
.010	.021	.054	.114	.177	.250	.500	
.012	.022	.062	.125	.187	.312	.562	

### TENSILE STRENGTH CHART<sup>A</sup>

Diameter, in	Tensile Strength, psi	
	minimum	maximum
Annealed		
Under 0.032	80,000	115,000
0.032 and over	80,000	105,000
Cold-worked, regular temper, all sizes	120,000	
Cold-worked, spring temper	.....	165,000
Up to 0.057 incl.	185,000	.....
Over 0.057 to 0.114 incl.	175,000	.....
Over 0.114 to 0.229 incl.	170,000	.....
Over 0.229 to 0.329 incl.	165,000	.....
Over 0.329 to 0.375 incl.	160,000	.....
Over 0.375 to 0.500 incl.	155,000	.....
Over 0.500 to 0.563 incl.	140,000	.....

<sup>A</sup> Tensile strengths not available for sizes larger than .563".

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Inconel 625 Spring Tempered Wire ASTM B446 UNS N06625	Cold drawn. Good corrosion resistance. Good for use in elevated temperature applications.	-	120	(E) 29 (G) 11.0	45%	.012" to .175"

### SIZE CHART

Wire Diameter, in					
.012	.033	.092	.112	.148	.207
.023	.054	.104	.120	.160	.562
.029	.091	.105	.135	.177	

#### COMMENTS:

There is currently not a standard/specification which covers tensile/yield strength values for spring tempered wire. Tensile strengths should be comparable to Inconel X750; however, please check with a Suhm representative for actual strength values.  
Larger sizes can be obtained in the spring tempered condition. Check with a Suhm representative for further information.

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range, ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Inconel 718 Spring Tempered Wire ASTM B637 UNS N07718	Age hardened. Good corrosion resistance. Good for use in elevated temperature applications. No magnetism	1200°F	250/210	(E) 29 (G) 11.2	45%	.012" to .275"

### SIZE CHART

Wire Diameter, in							
.012	.029	.045	.062	.080	.098	.128	.179
.014	.030	.046	.063	.082	.099	.129	.180
.015	.031	.047	.064	.083	.100	.135	.182
.016	.032	.049	.065	.084	.102	.138	.187
.017	.033	.050	.066	.085	.105	.140	.192
.018	.034	.051	.067	.086	.107	.141	.200
.019	.035	.052	.068	.087	.109	.142	.202
.020	.036	.053	.069	.088	.110	.144	.207
.021	.037	.054	.070	.089	.112	.148	.218
.022	.038	.055	.071	.090	.113	.156	.225
.023	.039	.056	.072	.091	.115	.157	.234
.024	.040	.057	.074	.092	.118	.162	.244
.025	.041	.058	.075	.093	.120	.165	.250
.026	.042	.059	.076	.094	.122	.170	.262
.027	.043	.060	.077	.095	.125	.172	.275
.028	.044	.061	.078	.097	.127	.177	

#### COMMENTS:

There is currently not a standard/specification which covers tensile/yield strength values for spring tempered wire. Tensile strength should be comparable to Inconel X750, however please check with a Suhm representative for actual strength values.

Larger sizes can be attained in the spring tempered conditions. Also bar stock is available in the solution annealed/aged condition. Check with a Suhm representative for further information.

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range, ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Inconel 718 Bar ASTM B637 UNS N07718	Age hardened. Good corrosion resistance. Good for use in elevated temperature applications. No magnetism.	1200 °F	250/210	(E) 29 (G) 11.2	45%	.234" to 1.500"

### SIZE CHART

Bar Diameter, in			
.234	.406	.687	.885
.250	.562	.734	1.420
.281	.573	.750	1.500
.359	.625	.875	

#### COMMENTS:

There is currently not a standard/specification which covers tensile/yield strength values for spring tempered wire. Tensile strength should be comparable to Inconel X750, however please check with a Suhm representative for actual strength values.

Larger sizes can be attained in the spring tempered conditions. Also bar stock is available in the solution annealed/aged condition. Check with a Suhm representative for further information.

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range, ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
MP35N Spring Tempered Wire AMS 5844 UNS R30035	Cold drawn, age hardened. High strength. High modulus value and corrosion resistance. Great choice for severe spring applications. Good for applications involving the presence of Hydrogen Sulfide.	600 °F	330/230	(E) 34 (G) 11.74	45%	.005" to .750"

### SIZE CHART

Wire Diameter, in							
.005	.017	.035	.058	.120	.177	.283	.562
.007	.018	.041	.062	.125	.187	.312	.625
.008	.021	.042	.072	.135	.192	.343	.750*
.009	.022	.044	.080	.142	.207	.375	
.010	.024	.045	.093	.148	.218	.406	
.012	.025	.048	.100	.156	.225	.437	
.014	.031	.050	.105	.162	.243	.468	
.015	.032	.054	.114	.172	.250	.500	

\* Larger sizes available.

### SS-MP35N

#### Suhm Coil Spring Works Wire Specification for MP35N

Suhm Spring Specification	Heat Treat	Notes
SS-MP35N	1200 °F Min. / 4 Hrs. Min.	Must meet and be certified to AMS-5844A Chemicals Only. Physical Properties are to meet SS-MP35N. Solution Heat Treat and Original Mill Required NACE MR-01-75-94. (HRC 55.0 Max)

#### Physical Properties for SS-MP35N after Drawn and Aged

Sizes	Minimum Tensile Strength, ksi	Minimum Yield, ksi	Minimum Elongation, %	Minimum Reduction of Area, %	HRC
.001 - .005	300	280	1.0	Report	40 - 55
.006 - .100	290	280	4	20	40 - 55
.101 - .170	280	270	4	20	40 - 55
.171 - .250	260	240	5	20	40 - 55
.251 - .437	240	230	6	20	40 - 55
.438 - Over	230	220	8	20	40 - 55

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range, ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Elgiloy Spring Tempered Wire AMS 5834 UNS R30003	Cold drawn. Very high fatigue strength and long life.	600°F	350/220	(E) 29.5 (G) 11.5	45%	.005" to .750"

### SIZE CHART

Wire Diameter, in							
.005	.021	.041	.062	.105	.155	.243	.468
.007	.022	.044	.065	.107	.156	.250	.500
.008	.023	.045	.067	.109	.162	.263	.531
.009	.024	.047	.072	.110	.172	.275	.562
.010	.025	.048	.073	.113	.177	.306	.625
.012	.028	.049	.080	.114	.187	.307	.750
.013	.030	.050	.085	.120	.192	.312	
.014	.031	.051	.089	.125	.200	.331	
.015	.032	.054	.091	.135	.207	.343	
.016	.035	.055	.093	.141	.218	.375	
.017	.037	.058	.098	.142	.225	.406	
.018	.040	.060	.100	.148	.242	.437	

### SS-ELGILOY

#### Suhm Coil Spring Works Wire Specification for Elgiloy

Suhm Spring Specification	Heat Treat	Notes
SS-ELGILOY	980°F Min. / 5 Hrs. Min.	Must meet and be certified to AMS-5834A Chemicals Only. Physical Properties are to meet SS-Elgiloy. Solution Heat Treat and Original Mill Required NACE MR-01-97 (HRC 60 Max.)

#### Physical Properties for SS-ELGILOY after Drawn and Aged

Sizes	Minimum Tensile Strength, ksi *	Minimum Yield Strength, ksi	Minimum Elongation, %	Reduction of Area, minimum, %	HRC
.001 - .005	330	290	1.5	Report	46 - 55
.006 - .100	300	290	1.5	Report	46 - 55
.101 - .125	290	280	4	20	46 - 55
.126 - .170	290	280	4	20	46 - 55
.171 - .250	260	240	4	20	46 - 55
.251 - .437	240	230	6	20	46 - 55
.438 - Over	230	220	8	20	46 - 55

\* Tensile strengths are not specified for sizes greater than .562

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range, ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Monel 400 Spring Tempered Wire AMS 7233 or 4544, ASTM B164 UNS N04400	Cold drawn. Good corrosion resistance. Good for elevated temperature applications.	450 °F	165/120	(E) 26 (G) 9.5	40%	.014" to .562"

### SIZE CHART

Wire Diameter, in							
.014	.052	.068	.085	.102	.140	.200	.331
.024	.053	.069	.086	.105	.142	.207	.343
.026	.054	.070	.088	.109	.148	.218	.362
.028	.055	.071	.089	.112	.156	.225	.375
.031	.056	.072	.090	.113	.162	.234	.393
.032	.057	.074	.091	.115	.168	.244	.406
.034	.058	.075	.092	.118	.170	.250	.437
.035	.059	.076	.093	.120	.172	.262	.468
.038	.060	.077	.094	.121	.177	.282	.500
.040	.061	.078	.095	.125	.179	.295	.562
.041	.062	.080	.097	.128	.180	.297	
.045	.064	.082	.098	.129	.182	.306	
.050	.065	.083	.099	.135	.187	.312	
.051	.067	.084	.100	.138	.192	.325	

### MECHANICAL PROPERTIES OF COLD-WORKED WIRE IN COIL<sup>A</sup> SPRING TEMPER

Diameter, in	Tensile Strength, psi	
	minimum	maximum
0.028 and less	165,000	.....
Over 0.028 to 0.057 incl.	160,000	.....
Over 0.057 to 0.114 incl.	150,000	.....
Over 0.114 to 0.312 incl.	140,000	.....
Over 0.312 to 0.375 incl.	135,000	.....
Over 0.375 to 0.500 incl.	130,000	.....
Over 0.500 to 0.563 incl.	120,000	.....

A Properties are not applicable to wire after straightening and cutting

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range, ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Monel K-500 Spring Tempered Wire/Bar QQ-N-286 AMS 4676C UNS N05500	Cold drawn. Very high corrosion resistance. Good for use in elevated temperature applications.	500°F	195/140	(E) 26 (G) 9.5	40%	.018" to 2.00"

### SIZE CHART

Wire Diameter, in						
.018	.038	.105	.177	.268	.393	.531
.027	.041	.125	.184	.281	.406	.562
.031	.062	.135	.236	.312	.437	.625
.033	.072	.148	.250	.331	.468	
.034	.080	.162	.262	.362	.500	
Bar Diameter, in						
.687	.750	.875	1.000	1.250	1.625	1.875
.718	.812	.937	1.125	1.500	1.750	2.000

### SPECIFICATIONS FOR MONEL K-500

Element	Minimum %	Maximum %
Nickel + Cobalt	63.00	70.00
Aluminum	2.00	4.00
Titanium	1.025	1.00
Iron	....	2.00
Manganese	....	1.50
Silicon	....	1.00
Cobalt (3.1.1)	....	1.00
Carbon	....	0.25
Zinc (3.1.1)	....	0.02
Phosphorus (3.1.1)	....	0.02
Sulfur	....	0.010
Tin (3.1.1)	....	0.006
Lead (3.1.1)	....	0.006
Copper	Remainder	Remainder

### TENSILE PROPERTIES

(after Precipitation Heat Treatment)

Tensile Strength, min	140,000 psi
Yield Strength at 0.2% Offset, min.	100,000 psi
Elongation in 2 in. or 4D, min	20% (3.3.1.2.1.1)

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.



## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range, ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Hastelloy C-276 Wire AMS B574 (Chem. only), AMS J470 UNS N10276	Good corrosion resistance to many acids and salts.	see comment	see comment	(E) 29.8 (G) 10.9	-	.012" to .437"

### SIZE CHART

Wire Diameter, in							
.012	.029	.045	.062	.083	.102	.156	.250
.014	.030	.046	.064	.084	.105	.162	.262
.015	.031	.047	.065	.085	.109	.170	.282
.016	.032	.049	.067	.086	.112	.172	.297
.017	.033	.050	.068	.088	.113	.177	.306
.018	.034	.051	.069	.089	.115	.179	.312
.019	.035	.052	.070	.090	.118	.180	.331
.020	.036	.053	.071	.091	.120	.182	.343
.021	.037	.054	.072	.092	.125	.187	.362
.022	.038	.055	.074	.093	.128	.192	.375
.023	.039	.056	.075	.094	.129	.200	.393
.024	.040	.057	.076	.095	.135	.207	.406
.025	.041	.058	.077	.097	.138	.218	.437
.026	.042	.059	.078	.098	.140	.225	
.027	.043	.060	.080	.099	.142	.234	
.028	.044	.061	.082	.100	.148	.244	

#### COMMENTS:

Note: There is not a specification which covers tensile/yield values for spring tempered wire. Check with a Suhm representative for actual strength values. tempered wire. Check with a Suhm representative for actual strength values. Larger size can be attained in spring tempered condition. Check with a Suhm representative for further information.

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Hastelloy B-2 ASTM B335 AMS J470 UNS N10665	Good corrosion resistance to many acids and salts.	see comment	see comment	(E) 28 (G) 8.0	-	.018" to .207"

### SIZE CHART

Wire Diameter, in					
.018	.030	.041	.109	.130	.177
.023	.032	.062	.120	.148	.193
.025	.038	.102	.128	.162	.207

#### COMMENTS:

Note: There is not a specification which covers tensile/yield values for spring tempered wire. Check with a Suhm representative for actual strength values. Larger size can be obtained in spring tempered condition. Check with a Suhm representative for further information.

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Titanium Beta-C AMS 4957 UNS R58640	Age hardened. Good ductility and toughness. Good fabricability, and good resistance to general corrosion. Good for environments containing Ferric Chloride, Sodium Chloride, Carbon Dioxide, and Hydrogen Sulfide.	600°F	190/180	(E) 15.4 (G) 5.9	45%	.005" to .625"

\* Larger sizes are available.

### SIZE CHART

Wire Diameter, in							
.005	.014	.025	.062	.125	.187	.312	.562
.007	.015	.032	.072	.135	.192	.343	.625
.008	.017	.045	.080	.148	.207	.375	
.009	.018	.048	.093	.156	.225	.406	
.010	.021	.050	.105	.162	.243	.437	
.012	.022	.054	.114	.177	.250	.500	

### TENSILE STRENGTH CHART

#### VALUES INDICATE COLD DRAWN AND AGED MATERIAL

Nominal Diameter, inches	Tensile Strength, psi	Elongation in 4D %, minimum	Reduction of Area %, min.
Up to 0.187, incl.	190,000 - 210,000	10	20
Over 0.187 to 0.375 incl.	185,000 - 205,000	10	20
Over 0.375 to 0.625 incl.	180,000 - 200,000	8	20

#### COMMENTS:

Material has been cold drawn 20 - 35% final reduction. Additional cold reduction may be possible to produce higher tensile/yield strength. Larger sizes can be obtained in spring tempered and annealed condition. Check with a Suhm representative for size and tensile strengths.

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range ksi min	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
Titanium 6Al-4V AMS 4965 UNS 56400	Age hardened. Good ductility and toughness. Good fabricability, and good resistance to general corrosion.	-	165	(E) 15.0 (G) 5.0	40%	.020" to .250"

### SIZE CHART

Wire Diameter, in						
.020	.026	.037	.062	.105	.162	.193
.022	.028	.038	.069	.127	.163	.225
.024	.033	.040	.080	.135	.170	.250
.025	.036	.045	.090	.142	.177	

### TENSILE PROPERTIES: VALUES INDICATE COLD DRAWN AND AGED MATERIAL

Nominal Diameter, in	Tensile Strength, minimum, psi	Elongation in 4D %, min.	Reduction of Area %, min.
Up to 0.250, incl.	165,000	10	20

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.

## Suhm Spring Works - Materials Properties

Material	Material Properties	Maximum Working Temp.	Ultimate Tensile Range, ksi	Modulus of Elasticity, psi 10 <sup>6</sup>	Approx. Design % of Ultimate Tensile (torsional)	Common Sizes, in
H-12 Tungsten Bar ASTM A681 (Chem. only) UNS T20812	Good for high temperature applications.	700 °F	187	(E) 30 (G) 11.0	45%	.500" to 2.250"

### SIZE CHART

Bar Diameter, in			
.500	.750	1.000	1.500
.531	.781	1.062	1.562
.562	.812	1.125	1.625
.593	.843	1.187	1.687
.625	.875	1.250	1.750
.656	.906	1.312	1.812
.687	.937	1.375	2.000
.718	.968	1.437	2.250

#### COMMENTS:

Material is produced in the "As Rolled" condition. Springs produced from wire size diameters are "Cold Wound" and Tempered. Springs produced from bar size diameters are "Hot Wound", quenched, and tempered. Each Hot Wound spring is hardness checked to insure proper hardness. Tempered hardness should range between 41R<sub>C</sub> and 49R<sub>C</sub>. Bar lengths range from 15' to 19'.

HRC 41 = 187,000 psi tensile

HRC 49 = 253,000 psi tensile

These data are provided as a reference guide only and are not intended for design purposes. Strength values and sizes are subject to change. Please check with a Suhm Spring representative for confirmation.